

MICROHARDNESS OF A DEFORMED COPPER SAMPLE WHEN IMPACTED ON A RIGID WALL

N.V. PAKHNUTOVA^{1,2}, E.N. BOYANGIN¹, O.A. SHKODA¹, S.A. ZELEPUGIN^{1,2}

¹*Tomsk Scientific Center of the Siberian Branch of the Russian Academy of Sciences, Tomsk, Russia*

²*National Research Tomsk State University, Tomsk, Russia*

One of the widely used method for evaluating the dynamic characteristics of metals and alloys is the Taylor impact test. This method relates the dynamic yield strength of a cylindrical sample material to its residual length after impact on a non-deformable target. Taylor impact test is commonly used to determine the yield strength [1-3] and select constitutive relations and constants in numerical simulations [2-4].

This paper presents the Taylor impact test conducted using a one-stage light-gas gun [5]. A copper cylinder (M1) with a length of 32 mm and a diameter of 7.8 mm was used as a sample. The mass of the sample was about 15 g. Throwing conditions were chosen to ensure that the velocity of the sample exiting the barrel ranged from 150 to 450 m/s. Samples after testing were cut into two parts along the axis of symmetry using a DK7732 CNC EDM Wire Cutting Machine. Microhardness of samples was determined on a PTM-3 hardness tester (GOST 9650-76) with a measurements error of 2%.

Figure 1 shows the microhardness measurements along the symmetry axis of a copper sample at different impact velocities.

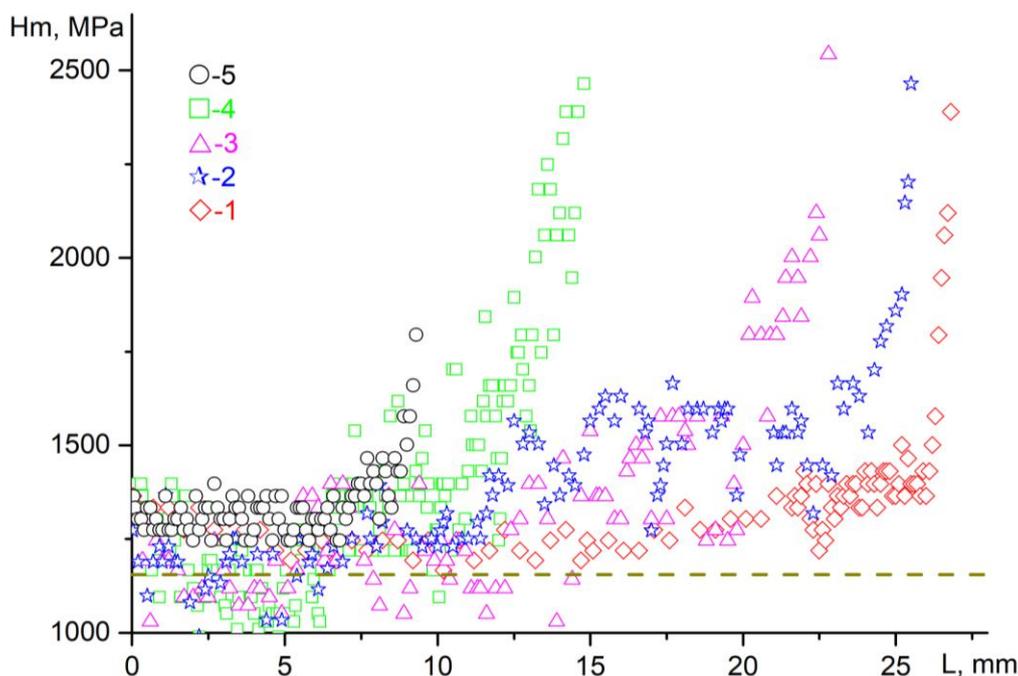


Fig.1. Distribution of microhardness along the axis of the samples at different impact velocities:
 (1) 162 m/s, (2) 167 m/s, (3) 225 m/s, (4) 316 m/s, (5) 416 m/s.

Non-linear changes in microhardness are observed along the sample axis after impact on the non-deformable target. For the starting sample, the average value of microhardness is 1155 MPa (Fig. 1, dashed line). The results in Fig. 1 show the higher microhardness at most points in the deformed state compared with the initial state.

REFERENCES

- [1] A.N. Bogomolov, V.A. Gorel'skii, S.A. Zelepugin, I.E. Khorev "Behavior of bodies of revolution in dynamic contact with a rigid wall", Journal of Applied Mechanics and Technical Physics, vol. 27, Issue 1, pp. 149-152, 1986. DOI: 10.1007/BF00911139.
- [2] E. Włodarczyk, M. Sarzynski "Strain energy method for determining dynamic yield stress in Taylor's test", Engineering Transactions, vol. 65(3), p. 499-511, 2017.
- [3] Y.V. Bayandin, D.A. Bilalov, S.V. Uvarov "Verification of wide-range constitutive relations for elastic-viscoplastic materials using taylor-hopkinson test", Computational Continuum Mechanics, vol. 13(4), p. 449-458, 2021. DOI: 10.7242/1999-6691/2020.13.4.35.
- [4] D.V. Yanov, A.S. Bodrov, N.V. Pakhnutova, S.A. Zelepugin "Simulation of dynamic channel-angular pressing of copper samples with allowance for experimental data of loading", Vestnik Tomskogo gosudarstvennogo universiteta. Matematika i mekhanika [Tomsk State University Journal of Mathematics and Mechanics], vol. 60. pp. 141-151, 2019. DOI: 10.17223/19988621/60/11.
- [5] Y.F. Khristenko, S.A. Zelepugin, A.V. Gerasimov "New light-gas guns for the high-velocity throwing of mechanical particles", ARPN Journal of Engineering and Applied Sciences, vol. 12, no. 22. P. 2017. 6606-6610.